

# Acousto-optical Characteristics of $\text{TeO}_3/\text{3C-SiC}/\text{LiNbO}_3$ layered structure

Namrata Dewan Soni\*

## Abstract

In the present work, use of thermally stable multi-layered  $\text{TeO}_3/\text{3C-SiC}/128^\circ\text{Y-XLiNbO}_3$  surface acoustic wave (SAW) structure, as a potential acousto-optic (AO) device has been proposed. The acoustic properties like figure of merit and diffraction efficiency of the layered structure  $\text{TeO}_3/\text{3C-SiC}/128^\circ\text{Y-XLiNbO}_3$  is examined using theoretical calculations. It is found that the thermally stable layered structure  $\text{TeO}_3(0.007\lambda)/\text{3C-SiC}(0.09\lambda)/128^\circ\text{Y-XLiNbO}_3$  exhibits a high value of acousto optical figure of merit ( $8.56 \times 10^{-12} \text{ s}^3 \text{ g}^{-1}$ ) coupled with good overlap between acoustic and optic field. The proposed acousto optic device is based on crystalline silicon carbide (SiC) which is known to withstand harsh environment. Thus the thermally stable  $\text{TeO}_3/\text{3C-SiC}/128^\circ\text{Y-XLiNbO}_3$  multi-layered SAW structure would be a potential and cost effective device suitable for acousto optic applications in severe environment conditions.

**PACS classification numbers:** Acoustic properties of thin films (43.35.+d) Thermal stability (68.60 Dv) Silicon carbide (61.80.Jh)

## 1. Introduction

The field of integrated optics uses a number of acousto optic (AO) devices like modulators, deflectors, tunable optical filters, optical switches, etc (Guofang et al. 2007; Jain et al. 1992; Kakio 2015; Mohammadalizadeh et al. 2010; Tsai et al. 1992). Efficiency of surface acoustic wave (SAW) devices used for AO applications banks upon the acousto-optical properties of the medium in which sound wave and light wave interact. Till now SAW devices based on  $\text{LiNbO}_3$ ,  $\text{LiTaO}_3$  single crystal and various layered structure like  $\text{TeO}_2/\text{LiNbO}_3$ ,  $\text{LiNbO}_3/\text{Sapphire}$ ,  $\text{ZnO}/\text{Diamond}$ , etc have been investigated (Belovickis et al. 2012; Guofang et al. 2007; Shandilya et al. 2008). Lack of flexibility in tailoring the SAW propagation characteristics like SAW phase velocity and temperature coefficient of delay (TCD) as per the need of the application, is the major limitation for the use of the single crystal based acoustic devices. On the other hand, it has been established that the use layered SAW structure provides more flexibility in tuning the various properties like TCD, phase velocity, coupling coefficient, etc of acoustic devices as per

the requirement (Dewan et al. 2008; Tsubochi et al. 1982; Tomar et al. 2001).

Recently, a temperature stable  $\text{TeO}_3/\text{3C-SiC}/128^\circ\text{Y-XLiNbO}_3$  multi-layered SAW structure has been found (Soni 2018), that possess high value of SAW phase velocity ( $\sim 4390 \text{ ms}^{-1}$ ) and electromechanical coupling coefficient ( $\sim 9.8\%$ ) at normalized over layer thickness of  $\text{TeO}_3 = 0.007\lambda$  and  $\text{3C-SiC} = 0.09\lambda$  (Soni 2018). This multi-layered SAW device is based on crystalline 3C-Silicon Carbide (SiC), which is a promising material for high frequency application and could sustain harsh environment (Mehregany et al. 2000). Since 3C SiC is being widely used in photonics and opto-electronics (Yamada et al. 2011; Liu et al. 1993), so in the present work an attempt has been made to investigate the acousto optic properties of the thermally stable  $\text{TeO}_3(\ )/\text{3C-SiC}(\ )/128^\circ\text{Y-XLiNbO}_3$  layered SAW device. The SAW propagation characteristics for the layered structure and the field profiles are calculated theoretically using the software developed by (Fahmy et al. 1975). The temperature stable  $\text{TeO}_3(\ )/\text{3C-SiC}(\ )/128^\circ\text{Y-XLiNbO}_3$  SAW structure is found to exhibit


\* Corresponding Author, Department of Physics, Hansraj College, University of Delhi, Delhi-110007, India  
Email: namratad20@gmail.com / ndsoni@hrc.du.ac.in

a high value of acousto optical (AO) figure of merit and high diffraction efficiency.

**Theoretical Calculations**


The possible use of TeO<sub>3</sub>( )/3C-SiC()/128°Y-X LiNbO<sub>3</sub> SAW layered structure in acousto optic devices is examined theoretically by calculating the

figure of merit and diffraction efficiency. The IDTs are placed on the top of 128°Y-X LiNbO<sub>3</sub> piezoelectric crystal. The configuration of TeO<sub>3</sub>( )/3C-SiC()/128°Y-X LiNbO<sub>3</sub> SAW layered structure studied for acousto-optic application is shown in figure 1.

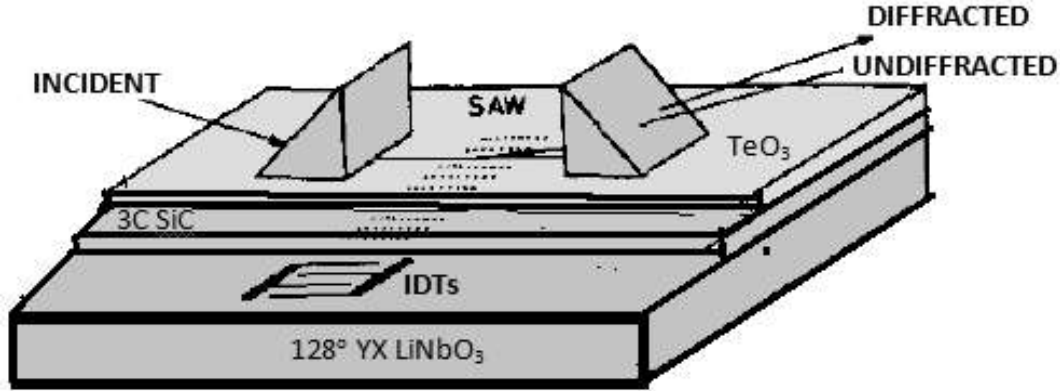

**Figure 1: TeO<sub>3</sub>( )/3C-SiC()/128°Y-X LiNbO<sub>3</sub> multilayered acousto optic device configuration with IDTs placed on the top of LiNbO<sub>3</sub> crystal.**

The required field profile and acoustic wave propagation characteristics of TeO<sub>3</sub>( )/3C-SiC()/128°Y-X LiNbO<sub>3</sub> layered structure has been calculated theoretically using the SAW program developed by Fahmy et al. 1975. The coordinate system used in the current work is given in figure 2. Here x<sub>1</sub> is the direction of propagation of surface wave whose amplitude vanishes as x<sub>3</sub> tends to negative of infinity.

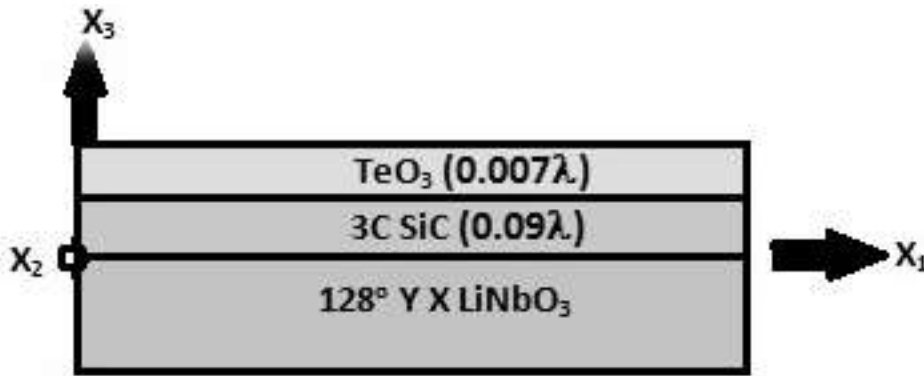

**Figure 2: The coordinate system used in the present work.**

The material parameters like elastic constants, density, refractive index, dielectric constant, photo elastic constants, etc used in the present study have been taken from the earlier reported work (Soni 2018).

**AO Figure of Merit**

The vital probe that determines the efficiency of an acousto optic device is its figure of merit. The figure of merit for the layered structure is defined as (Shandilya et al.2008)

$$M = \frac{n^6 p^2}{\rho v_p^3} \tag{1}$$

Where  $n$  and  $p$  are the respective appropriate photo elastic tensor and refractive index of wave guiding layer.

**Diffraction Efficiency**

Another important parameter for gauging the potential of an acousto optic device is its ability to diffract the optical signal i.e. diffraction efficiency and the latter can be calculated by (Rana et al. 2016):

$$DE = DE(f)_o^2 \left[ \frac{\sin \sqrt{DE(f)_o^2 + \left(\frac{K \Delta \theta L}{2}\right)^2}}{\sqrt{DE(f)_o^2 + \left(\frac{K \Delta \theta L}{2}\right)^2}} \right]^2 \tag{2}$$

Where,  $L$  is the interaction length or acoustic aperture,  $\lambda_0$  is the free space optical wavelength,  $\mathbf{k}$  is the momentum vector of SAW and  $\theta$  is variation of incident wave from the Bragg angle.

$$DE(f)_o^2 = \left(\frac{\pi}{\lambda_0}\right)^2 n_m n_n^2 |\Gamma_{mn}(f)|^2 \left(\frac{L}{\cos \theta_m \cos \theta_n}\right) \quad (3)$$

The AO diffraction efficiency varies directly with the overlap between the acoustic and optical fields. depends exclusively on the waveguide parameters and the acoustic frequency and is given by:

$$|\Gamma_{mn}(f)|^2 = \frac{[\int U_m(x_3) U_n(x_3) U_{ap} dx_3]^2}{\int |U_m|^2(x_3) dx_3 \int |U_n|^2(x_3) dx_3} \quad (4)$$

Where  $U_m$  represents field distributions of diffracted and un-diffracted modes respectively,  $p$  and  $r$  are appropriate photo elastic and electro optic tensor respectively. and  $U_m$  represent the normalized strain distributions along the waveguide thickness respectively, which have been calculated using the software developed by Fahmy et al. 1975 and a C program is written to calculate the overlap integral and hence the diffraction efficiency using equations (2), (3) and (4).

## Results and Discussions

### (I) Figure of merit

Figure 3 shows the dispersion of AO figure of merit for  $\text{TeO}_3/3\text{C-SiC}/128^\circ\text{Y-X LiNbO}_3$  layered

structure as a function of the normalized thickness of  $\text{TeO}_3$  layer. The value of AO figure of merit increases with an increase in the normalized thickness of  $\text{TeO}_3$  and becomes at zero TCD normalized thickness of 0.0071 of  $\text{TeO}_3$  over layer.

The increase in the value of acousto optic figure of merit with  $\text{TeO}_3$  over layer thickness is attributed to the fact that  $\text{TeO}_3$  possess lower surface acoustic wave velocity and with the increase in the  $\text{TeO}_3$  over layer thickness, SAW energy will be concentrated more into the  $\text{TeO}_3$  layer and therefore the SAW velocity of the layered structure decreases (Soni 2018). Since the AO figure of merit as given by equation (1) varies inversely the cube of SAW velocity, therefore with the increase  $\text{TeO}_3$  over layer thickness AO figure of merit increases. As reported earlier, with the integration of 0.007  $\text{TeO}_3$  over layer, the SAW layered structure  $\text{TeO}_3/3\text{C-SiC}/128^\circ\text{Y-X LiNbO}_3$  becomes thermally stable (Soni 2018) and temperature stability is an important aspect of an efficient SAW device. So the value of AO figure of merit is considered at 0.007  $\text{TeO}_3$  over layer thickness.

### (II) Diffraction Efficiency

Variation of diffraction efficiency with the optical penetration depth ( $x_3$ ) for  $\text{TeO}_3(0.007)/3\text{C-}$


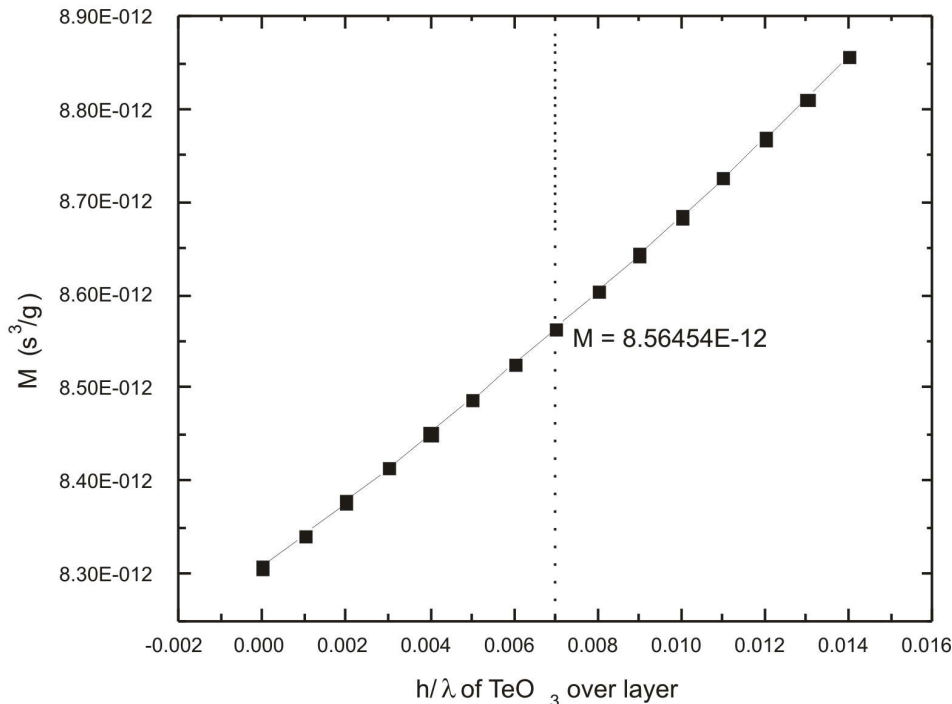


Figure 3: Variation of figure of merit with  $\text{TeO}_3$  over layer thickness in  $\text{TeO}_3/3\text{C-SiC}/128^\circ\text{Y-X LiNbO}_3$  SAW layered structure.

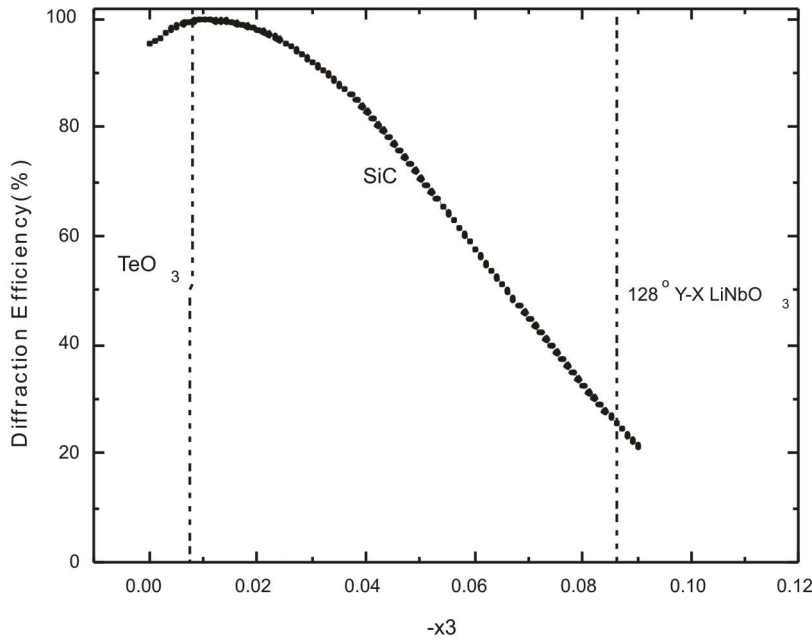

**Figure 4: Variation of Diffraction Efficiency with the optical penetration depth for  $\text{TeO}_3(0.007)/3\text{C-SiC}/128^\circ\text{Y-X LiNbO}_3$  layered structure**

$\text{SiC}/128^\circ\text{Y-X LiNbO}_3$  layered structure is shown in figure 4. The results show that the maximum overlap (nearly 100%) between acoustic and optical fields exists without  $\text{TeO}_3$  over layer. Diffraction efficiency is found to reduce slightly within 4% with the integration of temperature compensated 0.007  $\text{TeO}_3$  over layer. This slight decrease in the value of diffraction efficiency can be compromised for the temperature stability of the considered  $\text{TeO}_3(0.007)/3\text{C-SiC}/128^\circ\text{Y-X LiNbO}_3$  SAW device. Therefore, it is infer from the figure 4, that the temperature stable  $\text{TeO}_3(0.007)/3\text{C-SiC}/128^\circ\text{Y-X LiNbO}_3$  layered structure possess high value of diffraction efficiency (96.1%) indicating it to be boding device to be used in the acousto-optic applications.

#### Conclusion

In the present work the acousto optic characteristics of thermally stable  $\text{TeO}_3(0.007)/3\text{C-SiC}/128^\circ\text{Y-X LiNbO}_3$  layered structure have been examined theoretically. The  $\text{TeO}_3(0.007)/3\text{C-SiC}/128^\circ\text{Y-X LiNbO}_3$  SAW layered structure is found to be optimum for an efficient AO device with high AO figure of merit of coupled with high diffraction efficiency of 96%.

#### Acknowledgement

Author is extremely grateful to Dr.Rama Principal, Hans Raj College, University of Delhi.

#### References

1. Belovickis, J., Rimeika R., Ciplys D. (2012) Acousto-optic interaction with leaky surface acoustic waves in Y-cut LiTaO<sub>3</sub> crystals. *Ultrasonics*, 52(5), 593-597.
2. Colston G and Myronov M (2017) Controlling the optical properties of monocrystalline 3C-SiC heteroepitaxially grown on silicon at low temperatures. *Semiconductor Science and Technology*, 32, 114005(1-6).
3. Dewan N., Sreenivas K. and Gupta V. (2008) Theoretical studies on a  $\text{TeO}_2/\text{ZnO}/\text{diamond}$  layered structure for zero TD SAW devices. *Semiconductor Science and Technology*, 23, 1-6.
4. Fahmy A. H. and Adler E. L. (1975) Multilayer acoustic-surface-wave program. *Proceedings of the Institution of Electrical Engineers* 122, 470-472.
5. Guofang F., Jiping N., Jisheng Y. (2007) The design of  $\text{ZnO}/\text{LiNbO}_3$  thin-plating surface acoustical waveguide in acousto-optictunable filters. *Optics & Laser Technology*, 39(2) 421-423.
6. Jain S. and Mansingh A. (1992) Thin film layered structure for acousto optic devices *Journal of Physics D: Applied Physics*, 25, 1116-1121.

7. Kakio S. (2015) Acousto-Optic Modulator Driven by Surface Acoustic Waves. *Acta Physica Polonica A*, 127(1), 15-19 .
8. Kumar A. , Thachil G., Dutta S. (2019) Ultra high frequency acoustic wave propagation in fully polymer based surface acoustic wave device. *Sensors and Actuators A: Physical*, 292, 52- 59.
9. Liu Y. M. and Prucnal P. R. (1993) Low-loss silicon carbide optical waveguides for silicon-based optoelectronic devices. *IEEE Photonics Technology Letters*, 5(6), 704-707.
10. Mehregany M, Zorman CA, Roy S, Fleischman AJ, Wu CH and Rajan N (2000) Silicon carbide for microelectromechanical systems. *International Materials Reviews*, 45, 85-108.
11. Mohammadalizadeh D., Packirisamy M., Narayanswamy S. (2010) Stitched Acousto-Optic Modulator Stroboscopic Interferometry for characterizing larger microstructures. *Measurement*, 43(6), 810-821.
12. Rana L., Gupta V. , Dewan N., , Tomar M. (2016) SAW field and Acousto-optical Interaction in ZnO/AlN/Sapphire Structure. *Joint IEEE International Symposium on the Applications of Ferroelectrics*. <https://doi.org/10.1109/ISAF.2016.7578095>
13. Shandilya S, Sreenivas K, and Gupta V. (2008) Acousto optic and SAW propagation characteristics of a temperature stable multi-layered structures based on LiNbO<sub>3</sub> and diamond. *Journal of Physics D: Applied Physics*, 41, 1-6.
14. Soni N. D. (2018) SAW propagation characteristics of TeO<sub>3</sub>/3C-SiC/LiNbO<sub>3</sub> layered structure. *Materials research Express*, 5, 046309(1-5).
15. Takeuchi T., Amano H., Hiramatsu K., Sawaki N., Akasaki I., (1991) Growth of single crystalline GaN film on Si substrate using 3C-SiC as an intermediate layer. *Journal of Crystal Growth*, 115(1-4), 634-638.
16. Tomar M., Gupta V., Mansingh A., Sreenivas K. (2001) Temperature stability of c-axis oriented LiNbO<sub>3</sub>/SiO<sub>2</sub>/Si thin film layered structures. *Journal of Physics D: Applied Physics*, 34, 2267-2273.
17. Tsai C S and Lee P (1992) 4×4 non blocking integrated acousto-optic space switch. *Applied Physics Letters*, 60, 431-433.
18. Tsubochi K., Sugai K. and Mikoshiba (1982) Zero temperature coefficient surface acoustic wave devices using epitaxial AlN films. *Proceedings IEEE Ultrasonic Symposium*, 82, 340-345.
19. Yamada S., Song B. S., Asano T., and Noda S. (2011) Silicon carbide based photonic crystal nanocavities for ultra-broadband operation from infrared to visible wavelengths. *Applied Physics Letters*, 99(20), 201102(1-4).